

Description

The lamination systems with enhanced toughness without filling mediums, intended to be used for laminating of materials from glass, carbon, or Kevlar fibres. Letoxit PR 217 resin is produced on the basis of modified epoxy resin of Bisphenol A type.

The resin is considered to be physiologically well compatible. Hardeners are of amin type and do not contain nonylphenol. Due to the resin's low viscosity and thereby also lower interfacial tension it shows good wetting ability of lamination textiles and materials when combined in mixture with the Letoxit EM 315, EM 316, EM 317 hardening agents.

Application

Lamination compounds are intended to be used for production of components stressed in extreme conditions, e.g. aircraft and sail plane components, components for construction of models, gliders, construction of sporting boats, transport vehicle bodies, forms etc.

Lamination compounds are suitable for all types of manufacturing, such as manual laminating, winding as well as when using pressure or vacuum.

The optimum processing temperature of mixture lies in temperature range between 20 – 25°C. A higher processing temperature is also possible, but it shortens the pot-life of the compounds. The mixture pot-life lies between 45 minutes till 6 hours. Each hardener has got the same mixing ratio, therefore the hardeners can be combined by any way. This possibility enables to find optimal laminating system for various processing method. There is possible to take laminated part out of a mould after initiative curing for following working. Non-tacky, high-gloss surfaces are obtained even with unfavorable curing conditions such as lower temperatures or high relative humidity.

The mixture ratio must be followed as precisely as possible. Higher or lower dosage of the hardener does not result in acceleration or deceleration of the reaction, but leads to imperfect hardening and thereby also deterioration of mechanical properties. The mixture must be carried out properly. Mix it so long until the compound has no uniform transparent colour and until there are no unstirred hardener „clouds“. Laminating systems can be combined together with suitable gel coats, various lacquers and paints (for example based on PUR).

Resin specification

	Norm	Resin Letoxit® PR 217
Density at 25°C (g/cm ³)	PN-5M-11	1,13-1,15
Viscosity at 25°C (mPa.s)	PN-5M-01	900-1200
Epoxy equivalent	PN-5M-20	0,54-0,58
Epoxy value	-	170-185
Colour		yellowish

Hardener specification

	Norm	Hardener Letoxit® EM 315	Hardener Letoxit® EM 316	Hardener Letoxit® EM 317
Density at 25°C (g/cm ³)	PN-5M-11	0,94-0,97	0,94-0,97	0,93-0,96



APPLICATION METHOD

Letoxit® PR 217

Letoxit® EM 315, 316, 317

Version: 11/2011

Viscosity at 25°C (mPa.s)	PN-5M-01	50-100	60-120	100-140
Hydrogen equivalent	-	64	64	64
Amine value (mg KOH/g)	PN-5M-06	500-600	480-530	400-500
Colour	-	transparent blue	transparent blue	transparent blue

Processing details

	Letoxit® PR 217 + Letoxit® EM 315, 316, or 317
Processing temperature	20 – 30 °C
Viscosity of mixture at 25°C	500-900
Storage at 15 – 25 °C	minimally 6 months in their carefully sealed original containers
Curing	24 hours at temperature 20-25 °C
Post curing	15 hours at 50-60°C....up to..... 15 minutes at 150°C

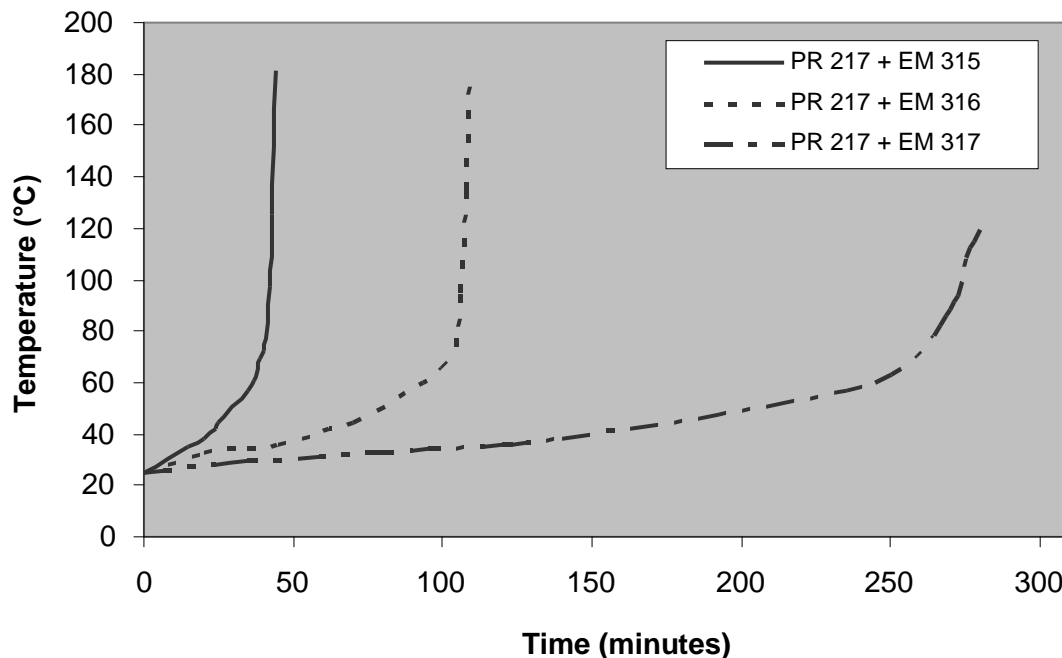
Mixture ratio

	Resin Letoxit® PR 217 : hardener Letoxit® EM 305, 306, 307
Parts by weight	100 : 37 ± 1
Parts by volume	100 : 45 ± 1

Version: 11/2011

Letoxit® PR 217
Letoxit® EM 315, 316, 317**Temperature rise**

100g at 25°C

**Gel time**

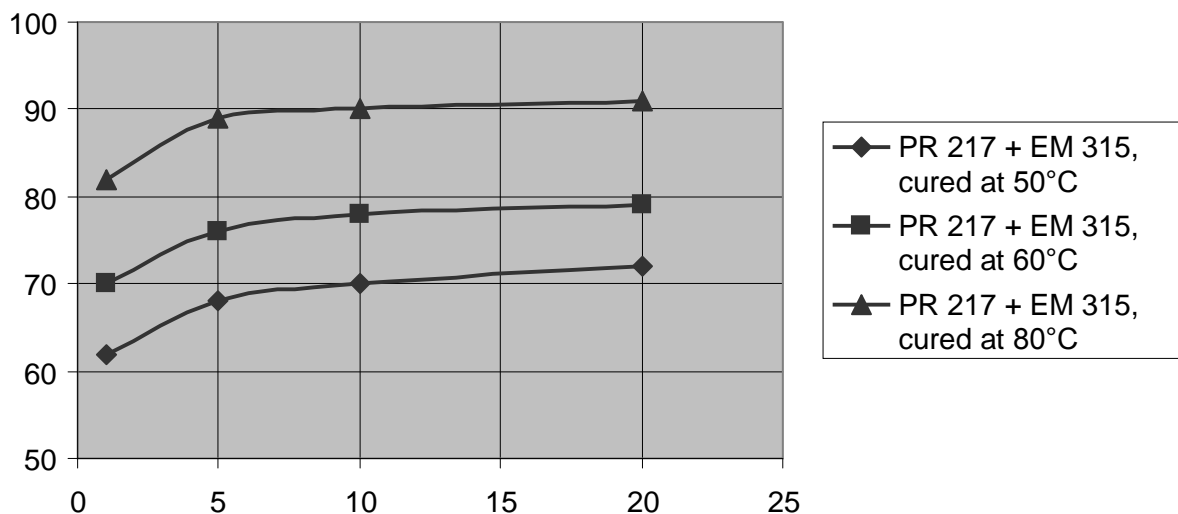
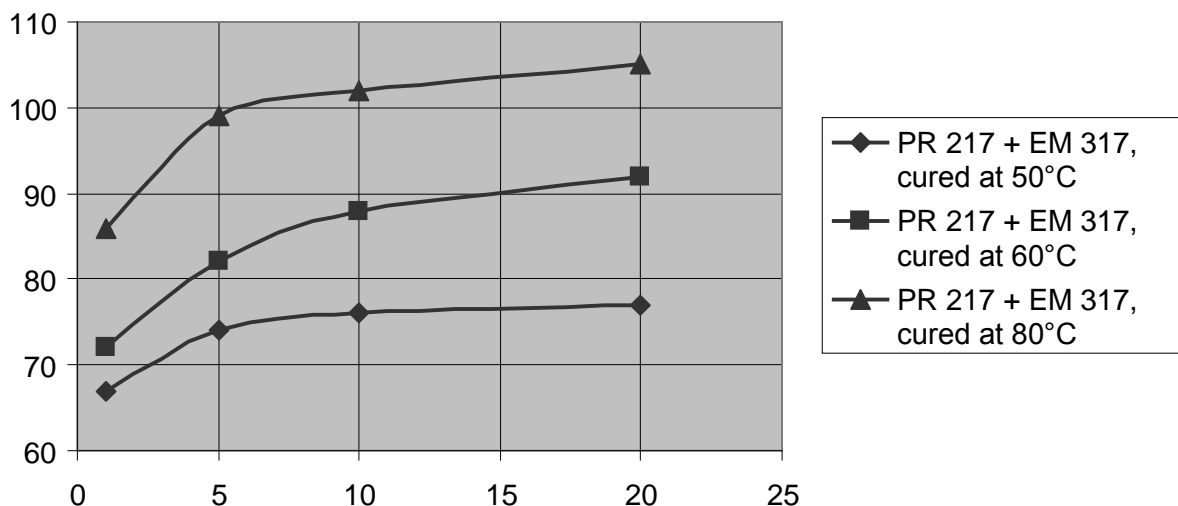
1 mm thick film at temperature 25°C

Letoxit PR 217 + Letoxit EM 315	Letoxit PR 217 + Letoxit EM 316	Letoxit PR 217 + Letoxit EM 317
2-3 hours	3-4 hours	6-7 hours

Glass transition temperature (T_g)

Curing	Letoxit® PR 217 Letoxit® EM 315	Letoxit® PR 217 Letoxit® EM 316	Letoxit® PR 217 Letoxit® EM 317
24 h 25°C + 15 h 60°C	75-80°C	85-90°C	90-95°C
24 h 25°C + 2 h 70°C + 10 h 120°C	-	-	130°C
24 h 25°C + 2 h 70°C + 10 h 120°C + 4 h 150°C	-	-	135°C

Version: 11/2011

Letoxit® PR 217
Letoxit® EM 315, 316, 317**Glass transition temperature rise (T_g)****Resin Letoxit PR 217 + hardener Letoxit EM 315****Resin Letoxit PR 217 + hardener Letoxit EM 317****Mechanical properties of unreinforced resin**

Curing: 24 h 25°C 2 h 70°C 6 h 120°C	Norm	Resin Letoxit PR 217 + hardener Letoxit EM 315, EM 316, EM 317
Density at 25 °C (g/cm³)	PN-5M-11	1,13-1,15
Flexural strength (MPa)	CSN EN ISO 178	110-120
Modulus of elasticity (GPa)	CSN EN ISO 178	3,0-3,3
Tensile strength (MPa)	CSN EN ISO 572	70-80
Compressive strength (MPa)	CSN EN ISO 604	120-140

Na Záhonech 1177
686 04 KUNOVICE
Czech Republictel: +420 572 433 711
fax: +420 572 433 700
email: 5M@5M.czwww.5M.cz
LETOXIT® is registered trademark of 5M s.r.o.

APPLICATION METHOD

Letoxit® PR 217

Letoxit® EM 315, 316, 317

Version: 11/2011

Impact strength (kJ/m²)	CSN EN ISO 179	55-65
Hardness Barcol (°Bc)	PN-5M-13	29

Packing

Resins and hardeners as well are supplied in PE containers in volume 2, 5, 10 or 20 kg and also in 200 kg drums.

